

## Polyaniline and Its Role on Thermal Stability, Viscoelastic Behavior and Electrical Conductivity of UV Curable Epoxy Resin

M. Alizadeh<sup>1</sup>, D. Zareei<sup>\*1</sup>, M. Ehsani<sup>2</sup>, R. Khajavi<sup>1</sup>, B. Shirkavand Hadavand<sup>\*\*3</sup>

<sup>1</sup> Technical Faculty, South Tehran Branch, Islamic Azad University, P.O. Box: 11365-4435, Tehran, Iran

<sup>2</sup> Department of Biomaterial, Iran Polymer and Petrochemical Institute (IPPI), P.O. Box: 14975-112, Tehran, Iran

<sup>3</sup> Department of Resin and Additives, Institute for Color Science and technology, P.O. Box: 16765-654, Tehran, Iran

### ARTICLE INFO

Article history:

Received: 12 Oct 2024

Final Revised: 03 Jan 2025

Accepted: 04 Jan 2025

Available online: 11 Mar 2025

Keywords:

Epoxy acrylate

Polyaniline

Thermal stability

Viscoelastic behavior

### ABSTRACT

*Ultraviolet (UV) curing systems have garnered significant attention and scholarly focus due to their remarkable ability to facilitate rapid curing processes while simultaneously exhibiting low energy consumption characteristics, which are increasingly pertinent in contemporary manufacturing and environmental sustainability discussions. The aim of this study is investigating the multifaceted role that polyaniline in UV-curable epoxy acrylate coatings. Both polyaniline and epoxy acrylate resin were synthesized through established chemical processes and subsequently characterized using a range of analytical techniques. To assess the impact of polyaniline on the epoxy acrylate resin, varying percentages of polyaniline, specifically at concentrations of 1, 3, and 5 %, were systematically incorporated into the epoxy acrylate resin matrix to evaluate their effects on the resultant material properties. A detailed analysis of the morphological characteristics of the prepared nanocomposites revealed a well-distributed and appropriate dispersion of polyaniline particles throughout the polymer matrix, which is crucial for achieving optimal performance in the final product. Thermal stability of the sample containing 3 % polyaniline exhibited a remarkable enhancement, being twice as high when compared to the sample that contained only 1 % polyaniline, thus highlighting the significance of polyaniline concentration on thermal properties. Furthermore, it was observed that the electrical conductivity of the sample incorporating 3 % polyaniline experienced a substantial increase, quantified at an impressive factor of 4.25 times greater than that of the sample with a lower concentration of 1 %, underscoring the enhanced electrical performance attributable to the optimized incorporation of polyaniline within the epoxy acrylate matrix. Prog. Color Colorants Coat. 18 (2025), 313-322© Institute for Color Science and Technology.*

### 1. Introduction

One of the common resins in the paint and coatings industry is epoxy resin, which has many applications due to its unique properties [1-3]. Epoxy resin is a two-component resin and needs a suitable hardener for

curing. The complete curing time is from a few hours to a few days, which can be accelerated by heating [4-7]. Although this process is accepted and used until now, in some cases the long curing time causes problems that the use of ultraviolet violet curing (UV-

\*Corresponding author: \* [d\\_zarei@azad.ac.ir](mailto:d_zarei@azad.ac.ir);

\*\*[shirkavand@icrc.ac.ir](mailto:shirkavand@icrc.ac.ir)

curing) systems is a suitable solution [8-11]. Increasing attention to UV curing systems due to the solvent-free system, quick curing, and low energy consumption has led to the creation of new applications for it and its use in various research and industrial sectors [12-15]. Many methods have been proposed in the field of the synthesis of UV curable resins, and in general, the synthetic processes are by acrylated resin with the help of suitable raw materials, which have a carbon-carbon end double bond and a catalyst [16-20].

A group of polymers such as polyacetylene (PA), polyaniline (PANi), polypyrrole (PPy) and polythiophenes (PTs) have a special structure that conducts electric current to pass through them and are known as conductive polymers. Blending conductive polymers with other polymers can lead to mixtures with special properties for specific applications. In fact, conductive polymers in the matrix of other polymers act like ways for the passage of electric current, the more these ways there are, the greater the electrical transmission ability. The electrical conductivity of conductive polymers can be changed by doping them or adding nanoparticles [21-24]. Polyaniline, celebrated for its unique features, is one of the most popular conductive polymers. It has a suitable performance for various applications including surface coatings. This polymer offers advantages such as excellent adhesion properties and good chemical stability and is suitable for coating on various surfaces [25, 26]. If polyaniline is used in nano dimensions, it can have different functions in the polymer substrate. Therefore, the distribution of polyaniline nanoparticles and their dimensions are effective in the electrical conductivity of the nanocomposite [27-29]. Polyaniline has the ability to perform reversible redox reactions and can act as a semiconductor and a conductor. For this reason, it is used as an anti-corrosion additive in coatings and for anti-static coatings and electromagnetic shielding applications [30, 31].

Based on a comprehensive review of existing literature, the incorporation of polyaniline within the matrix of epoxy acrylate resin remains unexamined, thereby necessitating further investigation in this specialized field. The primary objective of this research was to investigate strategies for the formulation of UV-curable epoxy acrylate nanocomposite coatings that incorporate polyaniline nanoparticles, with the intent of producing coatings characterized by rapid curing and economic efficiency. Furthermore, an evaluation of particle distribution has been performed through the

examination of morphological characteristics, electrical conductivity, and viscoelastic properties. The findings of this research may be advantageous in the development of sensors, UV-curable conductive adhesives, and coatings with corrosion resistance.

## 2. Experimental

### 2.1. Materials

Acrylic acid, triphenylphosphine, hydroquinone, aniline, ammonium persulfate, hydrochloric acid were obtained from Merck Co. (Germany). Epoxy resin KER 828 with a viscosity 13 Pa.s, at 25 °C and EEW 185-190 g/eq. was purchased from Kumho Co. (Korea). Moreover, diphenyl (2,4,6-trimethylbenzoyl)- phosphine Oxide (TPO), acting as a photoinitiator was sourced from Sigma-Aldrich Co. (USA).

### 2.2. Synthesis of epoxy acrylate resin

One mole of epoxy resin was added to a 500 mL three-necked round-bottom flask equipped with a mechanical stirrer, nitrogen inlet and drop funnel. The temperature of the balloon was elevated to 70 °C using an oil bath. An amount of 0.1 % triphenylphosphine as a catalyst and 0.1 % hydroquinone as an inhibitor was added to the flask and stirring was continued until a homogeneous mixture was reached. After homogenization, 2 moles of acrylic acid were added to the mixture by a drop funnel for 30 minutes, then the temperature rose to 90 °C and the reaction was persisted for 4 hours.

### 2.3. Synthesis of nano polyaniline

Polyaniline was prepared by oxidative polymerization of aniline in the presence of ammonium persulfate. In the first step, 2 mL of distilled aniline was stirred in 100 mL of 1 M hydrochloric acid solution for half an hour at room temperature. Then 40 mL of 1 M ammonium persulfate solution was gradually introduced to the reaction container and mixed for 5 hours at 0 °C temperature, then the reaction mixture was kept in the refrigerator for one day to complete the reaction. After filtering the sediment obtained, it was repeatedly washed with an aqueous solution of hydrochloric acid and dried in an oven for 10 hours. The obtained material was the conductive form of polyaniline (PANi) in emeraldine form.

### 2.4. Formulation of nanocomposites

Ratios of 1, 3 and 5 wt. % of synthesized polyaniline were added to epoxy acrylate resin. In the first step, the samples were mixed using sonication three times for 10 minutes to separate the polyaniline agglomerates and disperse them well in the epoxy acrylate resin. Then, 3 wt. % of Diphenyl (2,4,6-trimethylbenzoyl)-phosphine oxide (TPO), as a photoinitiator, was added to each sample and mixed with a magnetic stirrer until complete mixing. Polymer films with a thickness of 120 microns were applied on a steel substrate with a film applicator and cured using a UV-LED lamp for 1 minute.

### 2.5. Characterization

Fourier transform infrared (FT-IR) spectra were recorded on the Perkin-Elmer spectrophotometer, Spectrum 1 model (USA). The morphology was studied by PHILIPS scanning electron microscope (SEM) XL30 FEG. The viscoelastic behavior was

studied by dynamic mechanical thermal analyzer (DMTA), Netzsch, DMA 242 C (Germany). To conduct electrical conductivity, four-point conductivity test was performed according to the C611ASTM standard using the American-Precision Company's multimeter, model A5491, and the Meter Squrgedc (ITECH) company's power supply from China.

## 3. Results and Discussion

### 3.1. FTIR spectroscopy

Figure 1 shows the FTIR spectrum of polyaniline. The peak area of  $3443\text{ cm}^{-1}$  is characteristic of N-H in the structure and the peaks of  $2963$  and  $2927\text{ cm}^{-1}$  are related to aromatic C-H. The peaks in  $1638$  and  $1472\text{ cm}^{-1}$  correspond to the C=C bond in the quinone and benzoic rings, respectively. Also, the peaks at  $1294$  and  $1107\text{ cm}^{-1}$  indicate C-N in benzenoid. The peak area of  $804\text{ cm}^{-1}$  also characterizes the C-H bond.

Table 1: Naming samples and their percentage composition.

Sample	Epoxy acrylate (%)	TPO (%)	Polyaniline (%)
Blank	97	3	0
1 % PANi	96	3	1
3 % PANi	94	3	3
5 % PANi	92	3	5

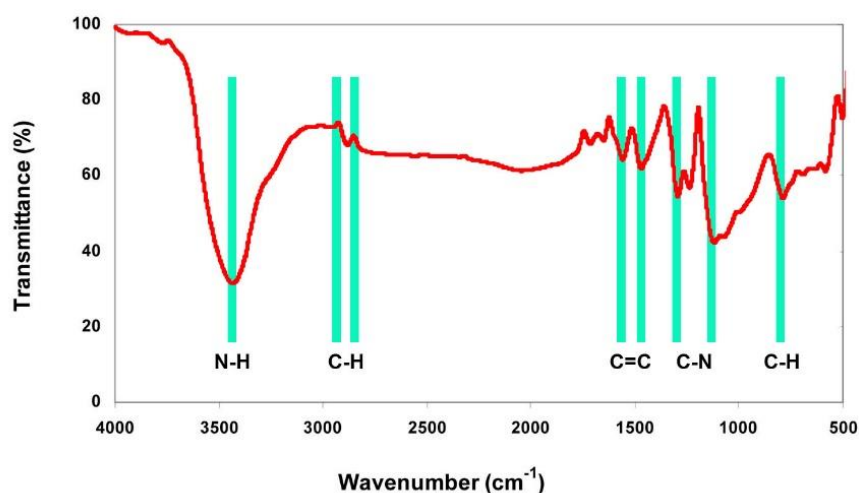


Figure 1: FTIR spectrum of polyaniline.

Figure 2 shows the spectrum of the synthesized epoxy acrylate. Within this Figure, the peak observed at  $3475\text{ cm}^{-1}$  corresponds to the elongation vibration of the hydroxyl group (OH), whereas the peaks at  $3104$  and  $2962\text{ cm}^{-1}$  are associated with the stretching vibration of aromatic and aliphatic C-H bonds, respectively. A carbonyl group (C=O) is evident at  $1723\text{ cm}^{-1}$ , and a C=C bond is present at  $1510\text{ cm}^{-1}$ , along with the C-O bond of the acrylate unit ether at  $1043\text{ cm}^{-1}$ . Consequently, it can be deduced that the epoxy acrylate resin has been successfully synthesized.

### 3.2. Morphology

Figure 3 shows the FE-SEM images of dispersed polyaniline (PANI) in an epoxy acrylate matrix. Samples, a, b and c contain 1, 3 and 5 % polyaniline, respectively. The results of the microscopic images indicate that the polyaniline particles are well

dispersed in the epoxy acrylate matrix. In the sample containing 1 % polyaniline, the particles are distributed homogeneously and without aggregation in the polymer matrix. With increasing the amount of polyaniline, a slight increase in the form of local aggregations is observed in the sample containing 3 % polyaniline. In the sample containing 5% polyaniline, an increase in the aggregation of polyaniline particles is observed. The formed aggregations can be attributed to the intrinsic properties of polyaniline and epoxy acrylate in terms of polarity. The conjugated structure of polyaniline has a rigid backbone. When introduced into a flexible matrix such as epoxy acrylate, the rigid chains tend to be placed together instead of uniformly dispersed and aggregations are formed. On the other hand, as the amount of polyaniline increases, the viscosity increases and mixing becomes more difficult and particle aggregations occur [32].

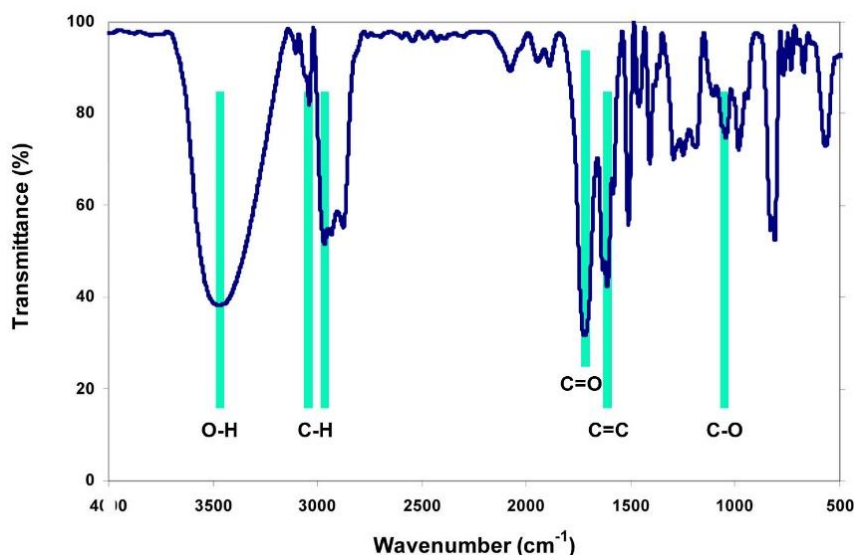


Figure 2: FTIR spectrum of epoxy acrylate resin.

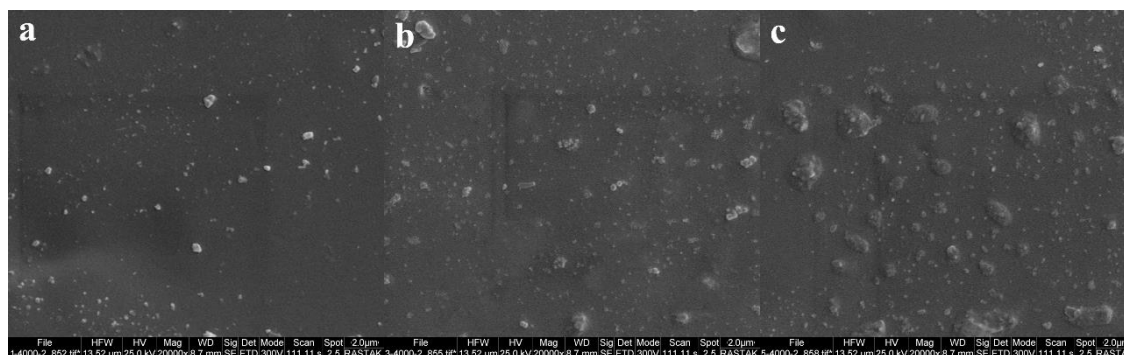


Figure 3: SEM images of epoxy acrylate/polyaniline nanocomposites. a: 1 %, b:3 % and c:5 %.

### 3.3. Electrical conductivity

Figure 4 shows the electrical transmission ability of the prepared nanocomposite coatings. As it is known, with the increase in the amount of PANi, the electrical transmission has increased. The quantity of this parameter in samples 1, 3 and 5 % PANi is  $2.09 \times 10^{-5}$ ,  $3.85 \times 10^{-5}$  and  $1.64 \times 10^{-4}$  S/cm, respectively.

Polyaniline is an intrinsically conductive polymer that can form continuous conductive networks in an epoxy matrix. When added at low percentages, it may be close to the diffusion threshold, forming the primary electron transport pathways. However, these pathways are sparse, leading to a modest increase in conductivity. As the polyaniline concentration increases, particle contact increases, forming more efficient continuous conductive pathways. At 5 %, the electrical conductivity increases as the interconnecting networks become more complete. On the other hand, polyaniline doped at low percentages carries a limited number of charge carriers, leading to a modest increase in conductivity. Further additions of doped polyaniline (5 %) have a higher electron density and maximize conductivity compared to 1 and 3 % polyaniline. The conductivity of the sample containing 5 % polyaniline is 4.25 times that of the 3% sample. The reason for this sudden increase is that it follows a diffusion model of electrical conductivity in composite materials. which increases dramatically once the critical concentration of polyaniline is reached. For this reason, for a sample containing 1 % polyaniline, there are only a few conductive paths, which leads to a small increase in conductivity. In the 3 % polyaniline sample, it is probably above the diffusion threshold, causing an increase in conductivity as the polyaniline particles are more closely connected and form a network. However, in the 5 % polyaniline sample, due to the increased network, it is above the diffusion threshold, and the conductivity reaches its maximum achievable level [33, 34].

### 3.4. Thermal stability

For the purpose of studying the thermal stability of prepared nanocomposites, a thermogravimetric test was used, and the DTG diagram is shown in Figure 5. As shown in figure 5, the losing weight for all samples takes place in three steps. The first stage takes place in the temperature range of 120-200 °C, which is related to the moisture present in the samples and unreacted materials. The second step of weight diminution is seen

at the temperature range of 260-380 °C, which is related to the degradation of polyaniline. With increasing temperature, the third stage of degradation takes place from 400-500 °C, in which epoxy acrylate resin is destroyed. It is also clear that the thermal stability increased with the increase of PANi amount, which can be explained by the intermolecular forces of PANi and epoxy acrylate [35-37].

A fall in the area under the graph in the DTG diagram indicates the formation of more stable compounds and a decrease in the liberation of volatile substances and the speed of the degradation reaction. As illustrated in Figure 5, the area under the curve decreases with escalating amounts of polyaniline and this indicates the stability of the nanocomposite, which increases due to the increase in polyaniline and its interactions with the epoxy acrylate polymer chains the degradation more difficult and increasing the thermal stability [38].

The addition of polyaniline to epoxy acrylate resin has increased thermal stability due to the creation of bonds between nanoparticles and polymer chains. The more these bonds, the higher the thermal stability, and therefore, with increasing polyaniline content, thermal stability has increased and the peak area under the curve has decreased, indicating increased thermal stability. Another factor that can be attributed to the increase in thermal stability and the decrease in the area under the curve is the strengthening of the polymer network and the reduction in the mobility of the polymer chains due to the presence of more polyaniline [39, 40].

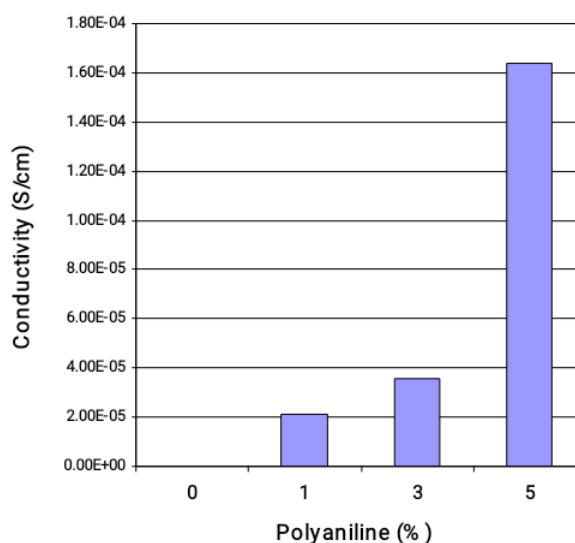


Figure 4: Comparison of electrical conductivity of epoxy acrylate coating with different percentages of PANi.

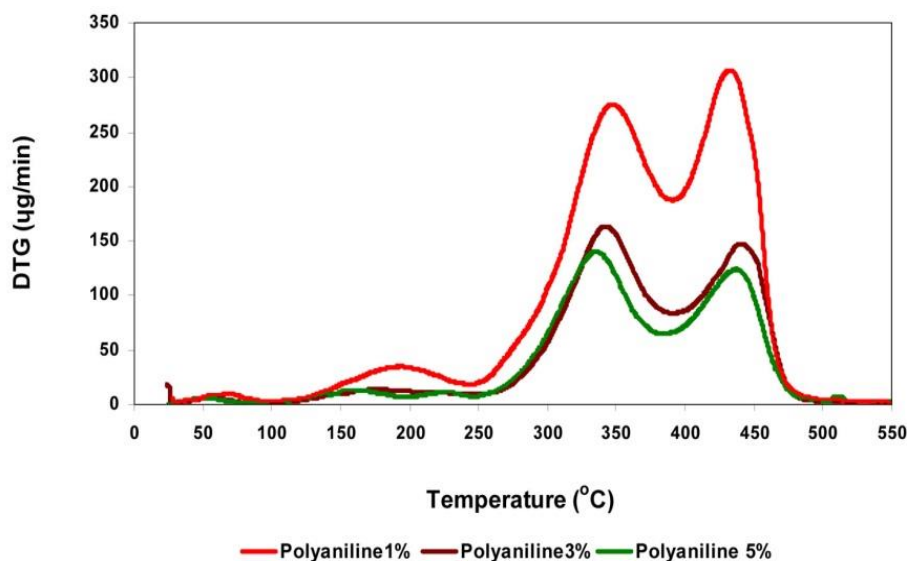


Figure 5: DTG diagram of epoxy acrylate/polyaniline nanocomposites.

### 3.5. Viscoelastic behavior

Figure 6 presents the elastic modulus ( $E'$ ) of resin samples composed of epoxy acrylate and polyaniline with varying proportions. The elastic modulus, also known as the modulus of elasticity or Young's modulus, is a measure of a material's stiffness and its ability to deform under stress. At lower concentrations of polyaniline (1 %), the elastic modulus of the cured nanocomposite may experience a moderate increase compared to the pure epoxy acrylate. Polyaniline, as a conductive polymer, can elevate the mechanical performance of the composite by providing additional reinforcement [41]. It forms a network within the epoxy matrix, improving stiffness and strength. With a higher concentration of polyaniline (3 %), there may be a more significant decrease in the elastic modulus, attributable to the correct distribution of polyaniline particles in the epoxy matrix.

The addition of polyaniline at this level enhances the interfacial interactions between the polymer matrix and the nanofiller. This improved compatibility can lead to better load transfer between the polymer matrix and the PANi, resulting in increased stiffness. At even higher concentrations of PANi (5 %), there might be a plateau or a slight decrease in the elastic modulus.

Beyond a certain concentration, the excessive amount of PANi might lead to agglomeration or clustering of the nanofillers, causing uneven distribution within the matrix. This clustering could create stress concentrations and defects, leading to a reduction in the overall stiffness.

Polyaniline, being a conductive polymer, can act as a reinforcing agent, enhancing the mechanical properties of the composite [42]. The concentration of PANi affects the quality of interfacial interactions between the polymer matrix and the nanofiller. Higher concentrations generally lead to better load transfer. At higher concentrations, the risk of agglomeration increases, causing uneven dispersion of PANi and potential negative effects on mechanical properties. There might be an optimal loading percentage where the positive effects on stiffness are maximized before diminishing returns or negative effects set in.

The loss modulus quantifies energy dissipation or damping characteristics of a material when subjected to deformation. As can be seen in Figure 7, at low temperatures, the loss modulus decreases with increasing polyaniline in the polymeric matrix because there are fewer nanoparticles and less molecular motion, and as a result, there is less mobility due to the friction between the polyaniline and the epoxy chain, so energy loss is reduced. Furthermore, at low temperatures, the thermal activation energy for molecular motion is usually higher, which limits motion and energy dissipation. At higher temperatures, the loss modulus increases due to the increased molecular mobility of polyaniline nanoparticles, which leads to increased friction and energy loss. In addition, at higher temperatures, the possibility of thermal excitations and molecular motion increases, which leads to more energy loss and thus an increase in the loss modulus [43]. In addition, at high temperatures,

structural changes such as polymer chain rearrangement or nanoparticle dispersion may occur, leading to changes in mechanical properties and consequently to changes in the loss modulus [44].

Figure 8 shows the diagram of  $\tan\delta$  for epoxy acrylate/polyaniline nanocomposites with different percentages of polyaniline. The presence of PANi in

epoxy resin increased the crosslink density by increasing the intermolecular interactions, and it is expected that the glass transition temperature also increases [45]. According to the results and as can be seen, the glass transition temperature shows an increase and for the blank sample, 1, 3 and 5 % PANi are equal to 77, 80, 87, and 93 °C respectively.

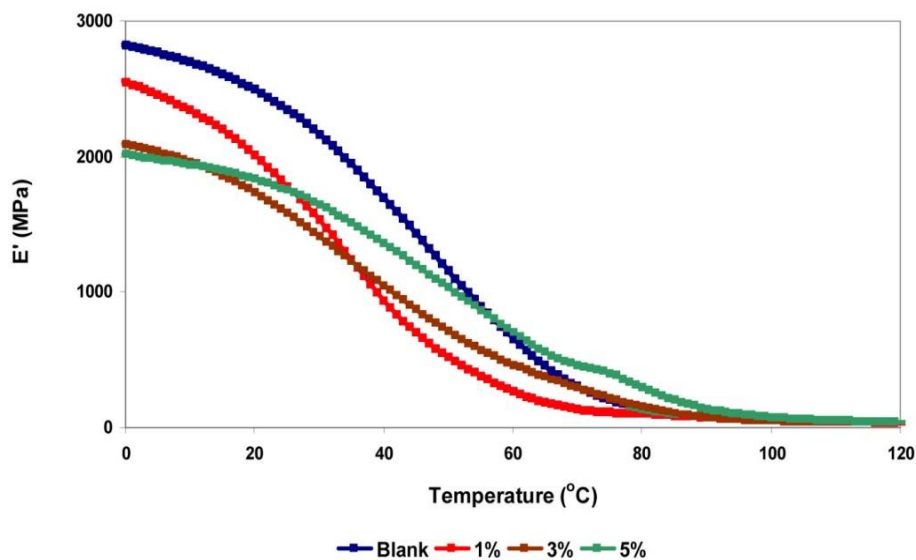


Figure 6: Elastic modulus of epoxy acrylate/polyaniline nanocomposites.

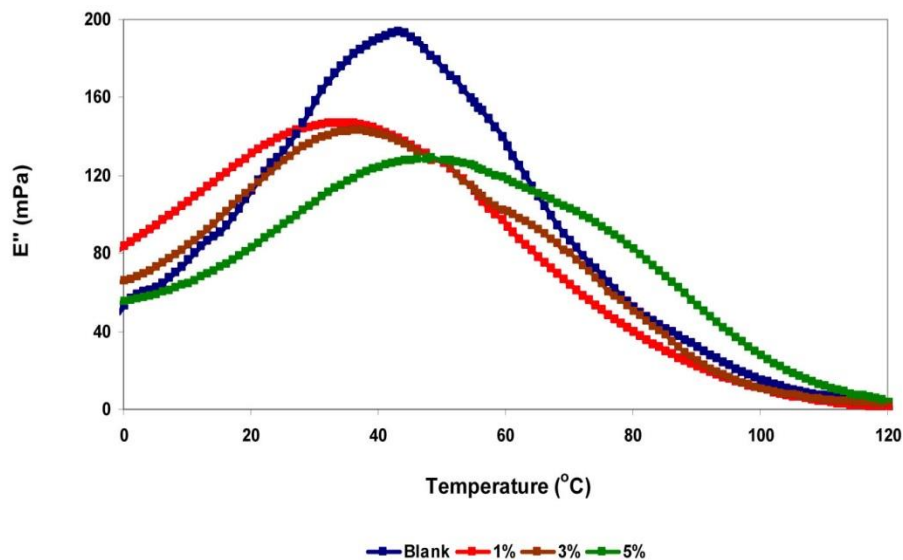
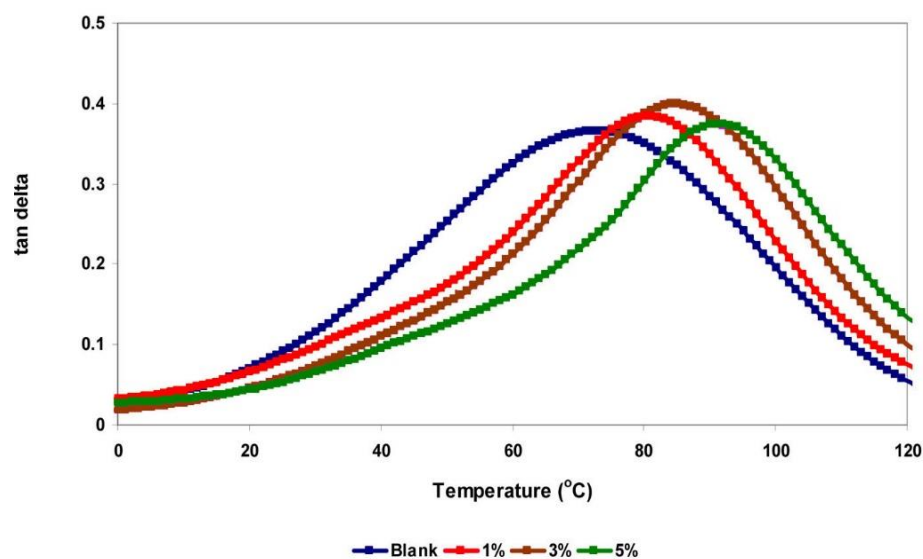


Figure 7: Loss modulus of epoxy acrylate/polyaniline nanocomposites with different percentages of polyaniline.



**Figure 8:** Diagram of  $\tan \delta$  for epoxy acrylate/polyaniline nanocomposites with different percentages of polyaniline.

#### 4. Conclusion

The results obtained from the spectroscopy analysis have effectively confirmed the successful synthesis of the UV-cured epoxy acrylate and also polyaniline resins. The obtained images of scanning electron microscopy (SEM) have provided visual evidence of the appropriate distribution of polyaniline particles within the epoxy matrix. Upon increasing the weight percentage of polyaniline from 3% by weight to 5% by weight, a notable improvement in electrical conductivity has been detected. The differential thermal analysis (DTG) diagrams have showcased the existence of three distinct

stages of weight loss, each corresponding to the presence of moisture and non-reacted materials, polyaniline, and epoxy acrylate, respectively. The thermal stability of the coating showed a great increase with the increase of polyaniline from 1 to 3 %, and for the 5 % sample, this increase was even greater. The elastic modulus decreased with the rise of polyaniline in the epoxy acrylate matrix and the loss modulus decreased at low temperatures and increased in warmer conditions. Also, the glass transition temperature of the sample without polyaniline, which was increased to 93°C in the sample containing 5 % polyaniline.

#### 5. References

1. Abniki M, Shirkavand Hadavand B, Najafi F, Fabrication of layered hydroxide composite with polydimethylsiloxane hydroxy-terminated for epoxy resin flame retardancy. *J Inorg Organomet Polym Mater.* 2023; 33:1946-1954. <https://doi.org/10.1007/s10904-023-02630-y>
2. Ou B, Wang Y, Lu Y. A review on fundamentals and strategy of epoxy-resin-based anticorrosive coating materials. *Polym-Plast Technol Mater.*2021;60(6):601-625.<https://doi.org/10.1080/25740881.2020.1819317>.
3. Shirkavand Hadavand B, Pishvaei M, Hosseinianisari M. The role of nanoclay on surface roughness and characteristics of epoxy polysulfide nanocomposite. *Prog Org Coat* 2019;131:60-66. <https://doi.org/10.1016/j.porgcoat.2019.02.024>.
4. Abniki M.; Shirkavand Hadavand B, Najafi F, Abniki M, Ghasedi I. Synthesis of the effective flame retardant via modification of epoxy resin with phenylboronic acid, *J Macromol Sci - Pure Appl Chem.* 2022; 59(6):411-420. <https://doi.org/10.1080/10601325.2022.2054349>.
5. Verma C, Olasunkanmi LO, Akpan ED, Quraishi MA, Dagdag O, El Gouri M, Ebenso EE, Epoxy resins as anticorrosive polymeric materials: A review. *React Funct Polym.* 2020;156:104741. <https://doi.org/10.1016/j.reactfunctpolym.2020.104741>.
6. Jouyandeh M, Ganjali MR, Shirkavand Hadavand B, Aghazadeh M, Akbari V, Shammiry F, Saeb MR. Curing epoxy with polyvinyl chloride (PVC) surface-functionalized  $\text{Co}_x\text{Fe}_{3-x}\text{O}_4$  nanoparticles. *Prog Org Coat.* 2019; 137:105364. <https://doi.org/10.1016/j.porgcoat.2019.105364>.
7. Jouyandeh M, Rahmati N, Movahedifar E, Shirkavand Hadavand B, Karami Z, Ghaffari, M, Taheri P, Bakhshandeh E, Vahabi H, Ganjali MR, Formela K, Saeb MR. Properties of nano- $\text{Fe}_3\text{O}_4$  incorporated



- epoxy coatings from Cure Index perspective. *Prog Org Coat.* 2019;133:220-228. <https://doi.org/10.1016/j.porgcoat.2019.04.034>
8. Shirkavand Hadavand B, Hosseini H. Investigation of viscoelastic properties and thermal behavior of photocurable epoxy acrylate nanocomposites. *Sci Eng Compos Mater.* 2017; 24(5):691-697. <https://doi.org/10.1515/secm-2015-0161>.
  9. Xiang Q, Xiao F. Applications of epoxy materials in pavement engineering. *Constr Build Mater.* 2020; 235:117529. <https://doi.org/10.1016/j.conbuildmat.2019.117529>.
  10. Amoozadeh P, Mohsen Sarrafi AH, Shirkavand Hadavand B, Niazi A, Konoz E. UV-curable hybrid hydrogels of carbon quantum dots: synthesis, characterizations and investigation of properties and rheological behavior. *Polym-Plast Technol Mater.* 2022; 61(18):2063-2072. <https://doi.org/10.1080/25740881.2022.2089580>.
  11. Madhi A, Shirkavand Hadavand B. Tri-functional bio-friendly cross-linker for UV-curable coatings: Synthesis and study of viscoelastic properties. *Prog Color Color Coat.* 2021;14(3):199-207. <https://doi.org/10.30509/pccc.2021.81713>.
  12. Soleimani-Gorgani A, Najafi F, Mohammadrezaei F, Shirkavand Hadavand B. Transparent water-based UV-curable urethane acrylate ink-jet ink, *Int J Polym Anal Charact.* 2021; 26(3):228-239. <https://doi.org/10.1080/1023666X.2021.1876457>
  13. Wang S, Wu Y, Dai J, Teng N, Peng Y, Cao L, Liu X. Making organic coatings greener: Renewable resource, solvent-free synthesis, UV curing and repairability. *Eur Polym J.* 2020;123:109439. <https://doi.org/10.1016/j.eurpolymj.2019.109439>.
  14. Shirkavand Hadavand B, Najafi F, Saeb MR, Malekian A. Hyperbranched polyesters urethane acrylate resin: A study on synthesis parameters and viscoelastic properties. *High Perform Polym.* 2017;29(6):651-662. <https://doi.org/10.1177/0954008317696566>.
  15. Yousefi-Limaee N, Shirkavand Hadavand B, Rahmani Z. Study the adsorption performance of methylene blue by modified UV-curable hydrogel/chitosan nanocomposite: Isotherm and kinetics approach, *Pigment Resin Technol.* 2023; 52(3):341-348. <https://doi.org/10.1108/PRT-04-2022-0045>.
  16. Madhi A, Shirkavand Hadavand B. Bio-based UV-curable urethane acrylate graphene nanocomposites: synthesis and properties. *SN Appl Sci.* 2020; 2(4):1-9. <https://doi.org/10.1007/s42452-020-2527-4>.
  17. Madhi A, Shirkavand Hadavand B. Eco-friendly castor oil-based UV-curable urethane acrylate zinc oxide nanocomposites: Synthesis and viscoelastic behavior. *J Compos Mater.* 2020;54:101-110. <https://doi.org/10.1177/0021998319858017>.
  18. Pojnar K, Pilch-Pitera B, Patil R. Progress in the development of acrylic resin-based powder coatings—an overview. *Polimery.* 2024;69(3):141-158. <https://doi.org/10.14314/polimery.2024.3.1>.
  19. Najafi F, Shirkavand Hadavand B, Pournamdar A. Trimethoxysilane-assisted UV-curable urethane acrylate as clear coating: From synthesis to properties. *Colloid Polym Sci.* 2017;295:1717-1728. <https://doi.org/10.1007/s00396-017-4139-0>
  20. Mohtadizadeh F, Zohuriaan-Mehr MJ, Shirkavand Hadavand B, Dehghan A. Tetra-functional epoxy-acrylate as crosslinker for UV curable resins: Synthesis, spectral, and thermo-mechanical studies. *Prog Org Coat* 2015, 89, 231-239. <https://doi.org/10.1016/j.porgcoat.2015.09.002>.
  21. Namsheer K, Sekhar Rout Ch. Conducting polymers: a comprehensive review on recent advances in synthesis, properties and applications. *RSC Adv.* 2021;11:5659-5697. <https://doi.org/10.1039/D0RA07800J>.
  22. Zhu K, Li J, Wang H, Fei G. Comparative study on anticorrosion enhancement of carboxylated and sulfonated self-doped polyaniline on waterborne epoxy coating. *J Macromol Sci - Pure Appl Chem.* 2020;A58(4):249-261. <https://doi.org/10.1080/10601325.2020.1842764>.
  23. Bazli L, Yusuf M, Farahani A, Kiamarzi M, Seyedhosseini Z, Nezhadmansari M, Iranpoor M. Application of composite conducting polymers for improving the corrosion behavior of various substrates: A Review. *J Compos Compd.* 2020;2(5): 228-240. <https://doi.org/10.29252/jcc.2.4.7>.
  24. Jadoun S, Pal Singh Chauhan N, Chinnam S, Aepuru R, Sathish M, Singh Chundawat N, Rahdar A. A Short Review on Conducting Polymer Nanocomposites. *Biomed Mater Devices.* 2023; 1:351-365. <https://doi.org/10.1007/s44174-022-00009-0>.
  25. Eskandari E, Kosari MR, Davood Abadi Farahani MH, Dasineh Khiavi N, Saeedikhani M, Katal R, Zarinejad MA. Review on polyaniline-based materials applications in heavy metals removal and catalytic processes, *Sep Purif Technol.* 2020; 231:115901. <https://doi.org/10.1016/j.seppur.2019.115901>
  26. Gao F, Mu J, Bi Z, Wang S, Li Z. Recent advances of polyaniline composites in anticorrosive coatings: A review. *Prog Org Coat.* 2021; 151:106071. <https://doi.org/10.1016/j.porgcoat.2020.106071>
  27. Masum Talukder M, Mizanur Rahman Khan M, Khairul Amin M. A review on polyaniline (PANI) based nanocomposites for water purification. *S Afr J Chem Eng.* 2023; 44:276-282. <https://doi.org/10.1016/j.sajce.2023.02.004>
  28. Rangel-Olivares FR, Arce-Estrada EM, Cabrera-Sierra R. Synthesis and characterization of polyaniline-based polymer nanocomposites as anti-corrosion coatings. *Coatings,* 2021; 11(6):653. <https://doi.org/10.3390/coatings11060653>
  29. Razak SIA, Rahman WAWA, Sharif NFA, Nayan NHM, Saidi MAA, Yahya MY. Polyaniline-coated kenaf core and its effect on the mechanical and electrical properties of epoxy resin. *Compos Interfaces.* 2013;20(8):611-622. <https://doi.org/10.1080/15685543.2013.821019>

30. Dhawan SK; Singh N, Venkatachalam S. Shielding effectiveness of conducting polyaniline coated fabrics at 101 GHz, *Synth Met.* 2001; 125(3):389-393. [https://doi.org/10.1016/S0379-6779\(01\)00478-7](https://doi.org/10.1016/S0379-6779(01)00478-7).
31. Dhawan SK, Singh N, Rodrigues D. Electromagnetic shielding behaviour of conducting polyaniline composites. *Sci Technol Adv Mater.* 2003; 4(2):105-113. [https://doi.org/10.1016/S1468-6996\(02\)00053-0](https://doi.org/10.1016/S1468-6996(02)00053-0)
32. Zhang Y, Shao Y, Liu X, Shi Ch, Wang Y, Meng G, Zeng X, Yang Y. A study on corrosion protection of different polyaniline coatings for mild steel. *Prog Org Coat.* 2017; 111:240-247. <https://doi.org/10.1016/j.porgcoat.2017.06.015>.
33. Beygisangchin M, Abdul Rashid S, Shafie S, Sadrolhosseini AR, Lim HN. Preparations, properties, and applications of polyaniline and polyaniline thin films-A review. *Polym (Basel).* 2021, 13(12):2003. doi: 10.3390/polym13122003. PMID: 34207392; PMCID: PMC8234317.
34. Sharma N, Singh A, Kumar N, Tiwari A, Lal M, Arya, S. A review on polyaniline and its composites: From synthesis to properties and progressive applications. *J Mater Sci,* 59, 6206-6244 (2024). <https://doi.org/10.1007/s10853-024-09562-z>
35. Belaabed B, Wojkiewicz JL, Lamouri S, El Kamchi N, Redon N. Thermomechanical behaviors and dielectric properties of polyaniline-doped para-toluene sulfonic acid/epoxy resin composites. *Polym Adv Technol.* 2011; 23(8):1194-1201. <https://doi.org/10.1002/pat.2029>
36. Kausar A. Versatile epoxy/polyaniline and derived nanocomposite: from strategic design to advance application. *Mater Res Innov.* 2021; 25(6):321-330. <https://doi.org/10.1080/14328917.2020.1813452>
37. Kunju AMR, Gopalakrishnan J. Polyaniline nanorod adsorbed on reduced graphene oxide nanosheet for enhanced dielectric, viscoelastic and thermal properties of epoxy nanocomposites. *Polym Eng Sci.* 2021; 61(6):1755-1772. <https://doi.org/10.1002/pen.25698>
38. Chattopadhyay DK, Sankar Panda S, Raju KVS. Thermal and mechanical properties of epoxy acrylate/methacrylates UV cured coatings. *Prog Org Coat.* 2005;54(1):10-19. <https://doi.org/10.1016/j.porgcoat.2004.12.007>
39. Li X, Liu X, Liu H, Liu X, He R, Meng S. Structure, morphology and anti-corrosion performance of polyaniline modified molybdenum sulfide/epoxy composite coating, *Colloids Surf A,* 2022; 639:128345. <https://doi.org/10.1016/j.colsurfa.2022.128345>.
40. Bashir Khan S, li N, Chen S, Liang J, Xiao C, Sun X, Influence of nanoparticle size on the mechanical and tribological characteristics of TiO<sub>2</sub> reinforced epoxy composites, *Journ Mater Res Technol,* 2023:6001-6015. <https://doi.org/10.1016/j.jmrt.2023.09.002>.
41. Goswami S, Nandy S, Fortunato E, Martins R. Polyaniline and its composites engineering: A class of multifunctional smart energy materials. *J Solid State Chem Part A.* 2023; 317:123679. <https://doi.org/10.1016/j.jssc.2022.123679>.
42. Wang H, Wu X, Qin X, Fei G, Sun L, Li Y, Wang M. Ultraflexible and mechanically strong polymer/polyaniline conductive interpenetrating nanocomposite via in situ polymerization of vinyl monomer. *Polymers.* 2021;13:2159. <https://doi.org/10.3390/polym13132159>.
43. Krzak A, Nowak AJ, Heljak M, Antonowicz J, Garg T, Sumption M. Mechanical and thermal analysis of duroplastic matrix composites over a range of temperatures. *Polymers.* 2024; 16:606. <https://doi.org/10.3390/polym16050606>.
44. Yang Y, Xian G, Li H, Sui L. Thermal aging of an anhydride-cured epoxy resin. *Polym Degrad Stab.* 2015;118:111-119. <https://doi.org/10.1016/j.polymdegradstab.2015.04.017>.
45. Rahmani Z, Mousavi M, Shirkavand Hadavand B, Petru M, Vosáhlo J, Rahimian Koloor SS. The role of urethane acrylate in improving the elasticity of nano chitosan UV-curable hydrogel nanocomposite, *Nano-Struct Nano-Objects.* 2024;39:101293. <https://doi.org/10.1016/j.nanoso.2024.101293>.

How to cite this article:

Alizadeh M, Zaarei D, Ehsani M, Khajavi R, Shirkavand Hadavand B. Polyaniline and Its Role on Thermal Stability, Viscoelastic Behavior and Electrical Conductivity of UV Curable Epoxy Resin. *Prog Color Colorants Coat.* 2025;18(3):313-322 . <https://doi.org/10.30509/pccc.2025.167399.1329>.

